

determining the fatigue stress concentration factor which differs from that in HCF zone which is mostly a zone of only elastic strain .

5 CONCLUDING REMARKS

From the reading-piece presented herein, the following concluding remarks can be derived:

- It is explained that well-known Goodman formula for determining the fatigue safety factor for certain CA stress cycling process is not correct if the component is previously subjected to static prestressing. The correct formula is derived and its use is suggested.
- The mentioned mistake doesn't affect the methods of LCF fatigue assessments based on Goodman line in Haigh diagram.
- The limiting value of static prestress is derived which results with critical fatigue safety factor.
- The simple formula for determining the fatigue life of a component for the certain CA stress cycling process and the certain static prestress is suggested.
- Application of the formulae obtained leads to more robust design, or – for the same design – to increasing the accuracy of assessments.

As presented, Goodman's imperfection in determining the fatigue safety factor in the presence of static prestress, arised from equalizing the mean stress and static prestress, is "on the safe side". That is why its application in fatigue assessments of structures, components and joints couldn't make any harm and that is why this imperfection has not been yet derogated. By author's opinion, this surplus of safety is also one of the reasons for achieving so great success in the service life prolonging of structures, components and joints by the tools of Fracture Mechanics in last few decades..

The same approach to fatigue safety factor determination can be also applied to the known Gerber's parabola, Soderberg's or any other criterion of fatigue failure which takes into account specific material, state of stressing or service conditions.

References:

- [1] Goodman J, *Mechanics Applied to Engineering*. London: Longmans; 1899.
- [2] Banantine JA, Comer J.J. & Handrock J.L. *Fundamentals of metal fatigue analyses (chapter 2)*, N Jersey: Prentice-Hall; 1990.
- [3] *Design of Machine Elements*, Lecture 16, Worcester Polytechnic Institute, Mech. Eng. Dept., 2010. (users.wpi.edu).
- [4] Peterson RE. *Stress concentration factors*. John Wiley & Sons, N York, London, Sydney, Toronto; 1974.
- [5] Shigley J.E, Mischke C.R, *Mechanical Engineering Design*, McGraw-Hill; N. York 1989.
- [6] Jelaska D. (1990). *General formula proposition for components fatigue strength evaluation (in Croatian)*. *Strojarstvo*; 32: pp. 255-62.
- [7] Jelaska D, Podrug S. (1998). *Estimation of fatigue strength at operational load*, *Proc. Int. Symp. Fatigue Des., Vol. 2*. Marquis, G., Solin J. (Eds), pp. 427-32, ISBN 951-38-4575-3, Julkaisija-Utgivare-Publisher, Espoo, May 1998.
- [8] Jelaska D. Operational Strength of Steady Preloaded Parts. *Materialove Inzinerstvo* 1999; 17: 6-10.

4 FATIGUE LIFE ESTIMATION

The problematic death with above is related to HCF and could be applied in a low cycle fatigue (LCF) if dealing with true stresses. In both cases it doesn't impact a fatigue life assessments, because all the stresses are then situated on the Goodman line and one has not to take into account a load line, it is has not to distinguish among mean stress and static prestress. Thus, a Manson, Morrow and other formulae for total strain, basically derived from Goodman line stay same also in the case of static prestressing and can be used for determining the fatigue life in the zone of LCF.

However, in the zone of HCF, the fatigue life can be determined in an extremely simple way. Namely, for a given amplitude σ_a and mean σ_m stresses, which lies on Goodman line because they are limiting stresses in the same time, regardless the mean stress comprehends the static prestress or not, the Goodman line in Haigh diagram is determined with points (σ_m, σ_a) and $(\sigma_F, 0)$, Fig. 7. Its equation is:

$$y = \frac{\sigma_a}{\sigma_m - \sigma_F} (x - \sigma_F). \quad (17)$$

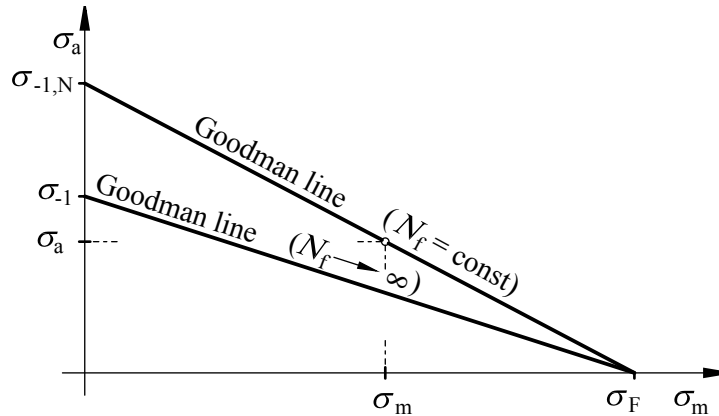


Fig. 7: Determining finite life Goodman line for the certain σ_a , σ_m and σ_F

The finite life fatigue strength $\sigma_{-1,N}$ represents the value of ordinate for zero abscissa:

$$\sigma_{-1,N} = \frac{\sigma_a \sigma_F}{\sigma_F - \sigma_m} = \frac{\sigma_a}{1 - \sigma_m / \sigma_F}. \quad (18)$$

The fatigue life is now obtained from the Woehler curve equation:

$$N_f = N_\infty \left(\frac{\sigma_{-1}}{\sigma_{-1,N}} \right)^m = N_\infty \left[\frac{\sigma_{-1}}{\sigma_a} (1 - \sigma_m / \sigma_F) \right]^m. \quad (19)$$

Like above, this expression is valid also for components having stress concentration. It is necessary than to correct σ_{-1} with fatigue stress concentration factor and, if needed, with size and surface factors. If dealing in LCF zone, similar procedure, but with true stresses, can also be applied for the estimation of the fatigue life. Since LCF zone is also a zone of elastic-plastic strains, the attention must than be paid to

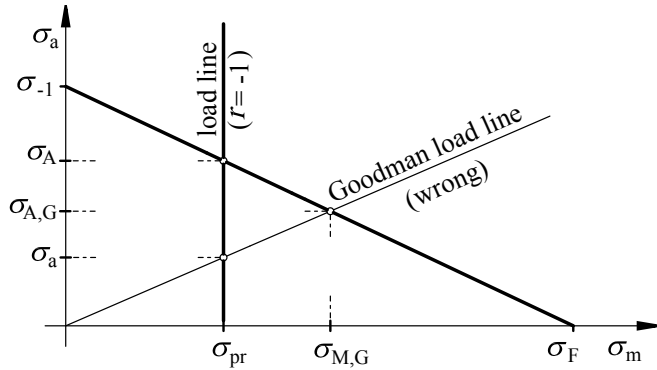


Fig. 4: Comparison of Goodman's and a real fatigue strength amplitude at the presence of static prestress and at $r = -1$ stress ratio of the source stress cycling

There is a limiting value $\sigma_{pr,b}$ of static prestress σ_{pr} for which the fatigue strength amplitude σ_A equals the stress amplitude σ_a , Fig. 5. For any $\sigma_{pr} > \sigma_{pr,b}$, σ_A becomes less than σ_a and fatigue safety factor less than one. It is not difficult to obtain $\sigma_{pr,b}$:

$$\sigma_{pr,b} = \sigma_F \left(1 - \frac{\sigma_a}{\sigma_{-1}}\right) - \sigma_m \quad (15)$$

Thus, the ratio $\sigma_{pr,b}/\sigma_{pr}$ could be also taken as fatigue safety factor, especially in some special, very rear cases, when amplitude stress stays constant by increasing the load.

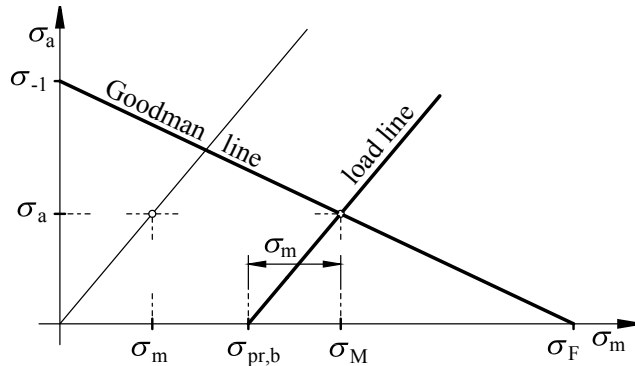


Fig. 5: Limiting value of static prestress

The correct formulae (7) and (8), just like (3) and (5), for determining the fatigue amplitude strength and fatigue safety factor can be applied also to the finite life of components. It is necessary only to change there the endurance limit σ_{-1} with finite life fatigue strength $\sigma_{-1,N}$ where latter is determined after Woehler (or Basquin):

$$\sigma_{-1,N} = \sigma_{-1} \left(N_\infty / N_f\right)^m \quad (16)$$

where N_f is the fatigue life expressed in the number of cycles and N_∞ and m are the fatigue life at the knee and the slope of the Woehler curve, respectively.

It is implied that in HCF calculations, the presented formulae can be used also if the stress concentration is present. It is necessary than only to correct the amplitude fatigue strength with fatigue stress concentration factor, and, if needed, with size and surface factors.

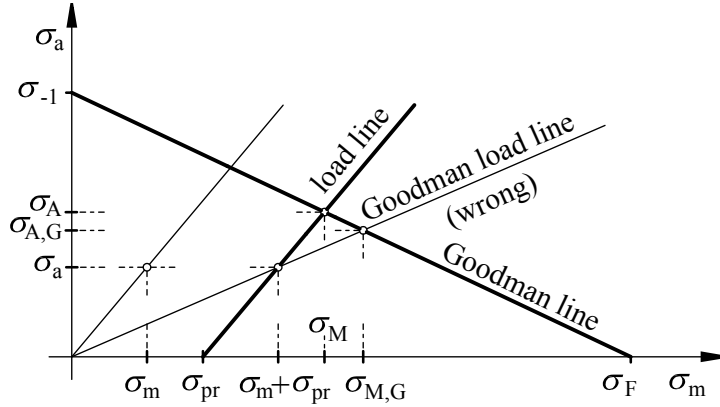


Fig. 3: Demonstration of wrong determination of fatigue strength after Goodman for statically prestressed components

Consequently, the known fatigue safety factor after Goodman is obtained once again:

$$s_{f,G} = \frac{\sigma_{A,G}}{\sigma_a} = \frac{1}{\frac{\sigma_a}{\sigma_{-1}} + \frac{\sigma_{pr} + \sigma_m}{\sigma_F}} \quad (10)$$

Obviously, in the presence of the static prestress, the fatigue strength amplitude $\sigma_{A,G}$ after Goodman is always less than the real one σ_A , for the same ratio as Goodman fatigue safety factors is less than the real one.

An extremely great mistake arises when the source stress process is of $r = -1$ stress ratio, Fig. 4. In such a case, the real fatigue strength amplitude is determined again by the intersection point of the Goodman line (1) and the load line $\sigma_m = \sigma_{pr}$. It is obtained:

$$\sigma_A = \frac{\sigma_{-1}}{\sigma_F} (\sigma_F - \sigma_{pr}) = \sigma_{-1} \left(1 - \frac{\sigma_{pr}}{\sigma_F}\right) \quad (11)$$

The real fatigue safety factor is:

$$s_f = \frac{\sigma_{-1}}{\sigma_a} \left(1 - \frac{\sigma_{pr}}{\sigma_F}\right) \quad (12)$$

After Goodman, the fatigue safety factor is then

$$s_{f,G} = \frac{1}{\frac{\sigma_a + \sigma_{pr}}{\sigma_{-1}} + \frac{\sigma_{pr}}{\sigma_F}} = \frac{\sigma_{-1}}{\sigma_a} \frac{1}{1 + \frac{\sigma_{pr} \sigma_{-1}}{\sigma_F \sigma_a}} \quad (13)$$

The ratio $s_f/s_{f,G} = \sigma_A/\sigma_{A,G}$ becomes

$$\frac{s_f}{s_{f,G}} = \left(1 - \frac{\sigma_{pr}}{\sigma_F}\right) \left(1 + \frac{\sigma_{pr} \sigma_{-1}}{\sigma_F \sigma_a}\right) \quad (14)$$

and obviously, it is much greater than one.

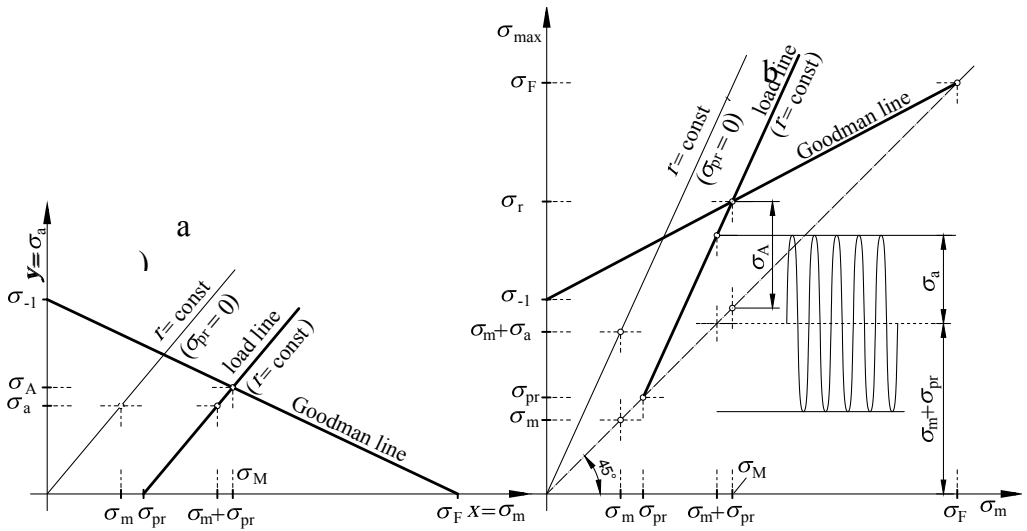


Fig. 2: Determining the fatigue strength in the presence of static prestress
a) in Haigh diagram b) in Smith diagram

The values of the σ_a and σ_m increase along the load line and its limiting values σ_A and σ_m , it is the fatigue strength, are determined (in Haigh diagram) with intersection point of the load line (6) and the Goodman line (1). So, solving Eqs. (1) and (6) yields:

$$\sigma_A = \frac{1 - \sigma_{pr}/\sigma_F}{\frac{1}{\sigma_{-1}} + \frac{\sigma_m}{\sigma_a \sigma_F}} = \frac{1 - \sigma_{pr}/\sigma_F}{\frac{1}{\sigma_{-1}} + \frac{1+r}{1-r} \frac{1}{\sigma_F}} \quad (7)$$

The fatigue safety factor is the ratio of limiting value σ_A of stress amplitude σ_a and the stress amplitude itself. It is obtained:

$$S_f = \frac{\sigma_A}{\sigma_a} = \frac{1 - \sigma_{pr}/\sigma_F}{\frac{\sigma_a + \sigma_m}{\sigma_{-1} \sigma_F}} \quad (8)$$

After Goodman, the limiting values $\sigma_{A,G}$ and $\sigma_{M,G}$ of σ_a and σ_m , it is the fatigue amplitude limit, is determined, as above, with intersection point of the Goodman line (1) and the straight line passing the origin of the Haigh diagram and the point $(\sigma_{pr} + \sigma_m, \sigma_a)$, see Fig. 3. In that figure, the latter straight line has been named as Goodman load line because it corresponds to Goodman safety factor. But, it cannot be a load line, because it is not the path along which the stresses increase! The static prestress cannot participate in load and stress increase, it stays same! Anyhow, after Goodman, it is obtained:

$$\sigma_{A,G} = \frac{\sigma_a}{\frac{\sigma_a + \sigma_{pr} + \sigma_m}{\sigma_{-1}} + \frac{\sigma_m}{\sigma_F}} \quad \sigma_{M,G} = \frac{\sigma_{-1}}{\frac{\sigma_a}{\sigma_{pr} + \sigma_m} + \frac{\sigma_{-1}}{\sigma_F}} \quad (9)$$

The limiting values σ_A and σ_M of σ_a and σ_m are the amplitude and mean stress of the fatigue strength respectively, which are determined with intersection point of the load line (2) and the Goodman line (1). Solving Eqs. (1) and (2) yields

$$y = \sigma_A = \frac{1}{\frac{1}{\sigma_{-1}} + \frac{\sigma_m}{\sigma_a \sigma_F}} = \frac{1}{\frac{1}{\sigma_{-1}} + \frac{1+r}{1-r} \frac{1}{\sigma_F}} \quad (3)$$

$$x = \sigma_M = \frac{1}{\frac{\sigma_a}{\sigma_m \sigma_{-1}} + \frac{1}{\sigma_F}} = \frac{1}{\frac{1-r}{1+r} \frac{1}{\sigma_{-1}} + \frac{1}{\sigma_F}} \quad (4)$$

where $r = \sigma_{\min} / \sigma_{\max}$ is a stress ratio (or a stress cycle assymetry factor). Obviously, σ_A and σ_M do not depend on σ_a and σ_m , but do depend on their ratio, it is on the stress ratio r .

The fatigue safety factor s_f here is equal to the ratio of σ_A and σ_a , but also, only in this simple case, to the ratio of $\sigma_A + \sigma_M$ and $\sigma_{\max} = \sigma_m + \sigma_a$ and to the ratio of σ_M and σ_m

$$s_f = \frac{\sigma_A}{\sigma_a} = \frac{\sigma_A + \sigma_M}{\sigma_m + \sigma_a} = \frac{\sigma_r}{\sigma_{\max}} = \frac{\sigma_M}{\sigma_m} = \frac{1}{\frac{\sigma_a}{\sigma_{-1}} + \frac{\sigma_m}{\sigma_F}} \quad (5)$$

where σ_r is the fatigue strength at r stress ratio, expressed in a term of maximum stress.

Obviously, the fatigue safety factor equals the Goodman safety factor, which means that Goodman's formula is valid for such a case of stressing.

3 FATIGUE STRENGTH AND SAFETY FACTOR IN THE CASE OF STATICAL PRESTRESSING

Goodman fatigue safety factor, as presented above, is generally accepted for any mean stress regardless of its nature, and here is hidden a mistake. Namely, when component is statically prestressed and after that subjected to the source (working) stress cycling process of the certain stress ratio r , the static prestress doesn't participate in load and stress increasing. Thus, static prestress σ_{pr} stays same and only the working mean stress σ_m and the amplitude stress σ_a of the source stress cycling process increase, of course, along the load line path which therefore has the same slope as the source stress cycling process has. So, the origin of the load line is moved for the value of mean stress along the abscissa (in Haigh diagram), Fig. 2a, and in the point $(\sigma_{pr}, \sigma_{pr})$ along the symetrale of Smith diagram, Fig. 2b. As Smith diagram has a possibility to present the stress states also in a time-stress diagram, it is more appropriate in order to demonstrate the states of all stresses and its changes.

Obviously, the load line in Haigh diagram passes the point $(\sigma_{pr}, 0)$ at the slope σ_a / σ_m . It is defined by equation

$$y = \frac{\sigma_a}{\sigma_m} (x - \sigma_{pr}) \quad (6)$$

of the mean and alternating stresses, but it is always a sum of static prestress and the source constant amplitude (CA) stress cycling process which generally has its own mean stress! The load increase doesn't affect the static prestress. It makes only the amplitude and the mean stresses of the source stress cycling process to increase along the path of the load line which origin is therefore moved along the abscissa of the Haigh diagram for the value of the static prestress, see Fig. 2. For a particular source stress cycling process the load line is a single one. In a word, all imperfections in determining the fatigue safety factor rises from no distinguishing among a mean stress and a static prestress. These imperfections had been perceived and the correct expression for the safety factor in the case of prestressed bolt had been offered by Shigley and Mischke [5], and correct general expression for determination the fatigue strength in the case of static prestressing had been obtained by author [6, 7, 8], but there were not enough reverberation in professional ambiances. That is a reason for this paper.

In the next sections the correct expressions for a fatigue safety factors is derived, compared with that after Goodman, and discussed.

2 FATIGUE STRENGTH AND SAFETY FACTOR IN THE ABSENCE OF STATIC PRESTRESS

In a simple case where the machine or structural (unnotched) component, joint or specimen are subjected to the CA stress cycling process with mean stress σ_m and amplitude stress σ_a , without static prestressing, the load straight line is determined with origin point (0, 0) of Haigh diagram and its slope σ_a/σ_m , see Fig. 1. The stressess σ_a and σ_m vary along the load line (which is also a line of constant stress ratio r). Its equation is

$$y = \frac{\sigma_a}{\sigma_m} x . \tag{2}$$

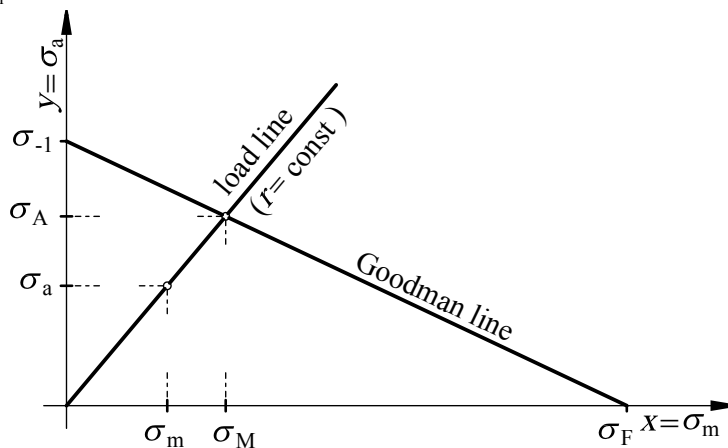


Fig. 1: Determining the fatigue strength when no static prestress is present

ON THE GOODMAN'S FATIGUE SAFETY FACTOR

Jelaska, D.

Abstract: It is demonstrated that, in the presence of static prestress, the fatigue strength amplitude calculated after Goodman's criterion is less than the real one. The mistake insight is on the "safe side" in fatigue design computations, but still wrong. This imperfection had been perceived and the unique, general formula for determining the fatigue safety factor in the presence of static prestress is offered. It is also presented the extremely simple way for determining the HCF life for known S-N curve and mean and amplitude stresses, on the basis of Goodman line in Haigh diagram.

Keywords: Haigh diagram, static prestress, load line, fatigue strength amplitude.

1 INTRODUCTION

Machine parts, structural components and joints are frequently subjected to the high cycle fatigue (HCF) stress cycling process and therefore the stress approach to fatigue design is suitable. This approach has been based on the concept of Goodman (straight) line [1] in Haigh diagram and corresponding fatigue safety factor. Goodman line is based on a huge number of testings and it is more or less unquestionable and generally accepted in design community. It is a locus of fatigue fracture states, i. e. a locus of limiting values of amplitude stresses for the certain mean stress or conversely. It connects the end points $(0, \sigma_{-1})$ and $(\sigma_F, 0)$ of Haigh diagram, where σ_{-1} is the endurance limit at stress ratio $r = \sigma_{\min}/\sigma_{\max} = -1$ and σ_F is some static property of material strength (originally by Goodman [1] – ultimate strength), see Fig. 1. Consequently, the safety factor for any point of this line equals unity. For any mean stress x and corresponding amplitude stress y , its equation is

$$y = \frac{\sigma_{-1}}{\sigma_F} (\sigma_F - x) . \quad (1)$$

A problem arises when determining a point of Goodman line which gives a correct limit value of the stress amplitude is bypassed after Goodman, because one has not to determine the fatigue strength amplitude in order to get the safety factor. Thus, the imperfections rising from no distinguishing among the mean stress and statical prestress remain in this concept and the well-known Goodman's formula of fatigue safety factor for the certain mean and amplitude stresses is still in use.

The mentioned imperfection had been perceived and the concept of the load line has been introduced in fatigue calculations, e.g. [2, 3, 4]. Following this concepts, the fatigue strength is determined with intersection point of the load line and the Goodman line. However, it didn't result with the an unique analytical expression for determining the correct value of the fatigue strength. The reason is simple: the authors didn't perceive that the resulting stress history of some component is not only a simple sum